



Group	220 – Polyester Low Bake – Low Thickness
Curing	min: 160°C @ 20' to 40' max: 190°C @ 6' to 11'
Surface	High Gloss - good leveling and appearance
Gloss	85 - 95 (60°)
Approvals	

PRODUCT DESCRIPTION

A gloss finish, low bake TGIC-free thermosetting polyester powder coating featuring excellent resistance to UV radiation and outdoor weathering. The powder forms a protective and decorative film with good outdoor resistance.

The high hiding power and excellent flow allow improved coverage as thinner films can be applied to achieve a pleasing aesthetic effect.

The low bake feature makes the product suitable for use on high speed tracks and for coating heavy gauge components.

Storage Life:

Store at temperatures lower than 30°C. Storage life in original package: 18 months.

CHARACTERISTICS

Spec. Gravity (kg/l): 1,25 – 1,65
DFT (micron): 40 - 60
Theoretical Coverage @40um: 19 m²/kg

Recommended film thickness:

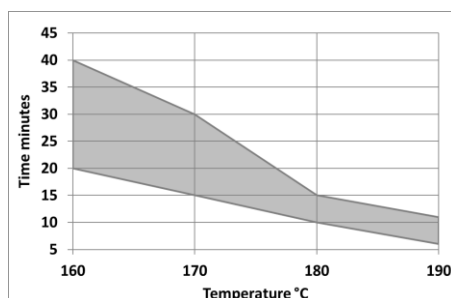
- Dry: 40 - 60 µm

APPLICATION

Suitable for automatic and manual electrostatic application. Please contact your Sherwin-Williams representative to discuss tribo-static application.

Curing Cycles

Time	Substrate temperature
6 – 11 min	190°C
10 - 15 min	180°C
15 - 30 min	170°C
20 - 40 min	160°C

**CHEMICAL RESISTANCE**

Immersion method for 48 hours at ambient temperature into:

CHEMICAL	RESULT
Hydrogen chloride 10%	intact
Nitric acid 30%	intact
Saturated hydrogen sulphide	intact
Hydrogen peroxide 40 volumes	intact
Ammonium hydroxide 10%	intact
Ammonium hydroxide 33%	intact
Sodium hydroxide 5%	intact
Tartaric acid 5%	intact
Citric acid 5%	intact
Lactic acid 5%	intact
Ethanol	intact
N-butanol	intact
Petroleum ether	slightly softened

SUBSTRATE PREPARATION

The surface treatment should be chosen according to the type of substrate and the required performance.

The surface to be coated must be free from oxidation, oil, grease or any other form of contamination.

A good quality pretreatment process is recommended for optimum performance.

Final user should select the proper pretreatment based on corrosion resistance performance.

Where required, the corrosion resistance can be enhanced using a primer system.

		Substrate				
Pretreatment		Aluminum	Steel	Galvanized Steel	Metallized Steel	Steel
Chemical	Cr-free (Zr, Ti, Oxilanes or alternatives)	✓		✓		
	Pre-anodising	✓				
	Chromate	✓		✓		
	Phospho-chromate	✓				
	Iron phosphate		✓			
	Zinc phosphate		✓	✓		
	Nano-ceramic		✓			
Mechanical	Sand blasting		✓			
	Soft blasting			✓	✓	
	Sweeping			✓	✓	

PERFORMANCE DATA

A 40um coating applied to a zinc phosphated steel test panel (UNI sheet) cured 20 minutes at 160°C satisfied the following requirements,

Gloss 60° :

85 - 95

UNI EN ISO 2813:2014

Buchholz indentation test:

more than 90

UNI EN ISO 2815

Pendulum-rocker hardness :

Perso pendulum

more than 300

UNI EN ISO 1522

Erichsen cupping test (mm):

more than 5

UNI EN ISO 1520

Direct impact test (cm.Kg):

more than 25

ASTM D 2794; ISO 6272-2:2002

Reverse impact test (cm.kg):

more than 25

ASTM D 2794; ISO 6272-2:2002

Conical mandrel : Bend test

Maximum 10mm

UNI EN ISO 6860

Crosscut adhesion (2mm) (GT):

Class 0

UNI EN ISO 2409

Salt fog test :

1000 hours

Scribe creep 3-6 mm

UNI ISO 9227

Resistance to humidity:

(Humidity test) 500 hours

no change

UNI EN ISO 6270-2:2005

CAUTION**FOR INDUSTRIAL SHOP APPLICATION**

Thoroughly review product label and Safety Data Sheet (SDS) prior to using this product.

A Safety Data Sheet is available from your local Sherwin-Williams facility or distributor

Note: Product Data Sheets are periodically updated to reflect new information relating to the product. It is important that the user obtain the most recent Product Data Sheet for the product being used. The information, rating, and opinions stated here pertain to the material currently offered and represent the results of tests believed to be reliable. However, due to variations in user handling and methods of application which are not known or under our control, The Sherwin-Williams Company cannot make any warranties as to the end result.